

# Influence of sintering temperature on the performance of titanium dioxide anode in Dye Sensitized Solar Cells with natural pigment hypericin

Katarina Cvetanović Zobenica, Nenad Tadić, Uroš Lačnjevac, Evgenija Milinković, Milena Rašljić Rafajilović, Milče M. Smiljanić, Dana Vasiljević-Radović, Dragomir Stanisavljev

**Abstract**—Dye Sensitized Solar cells (DSSC) are very attractive due to their low cost fabricating methods and used materials. One of the most important parts of the cells is the photoanode. Many semiconducting materials are used for this purpose, but most common one is titanium dioxide ( $\text{TiO}_2$ ). Optimal sintering temperature of anode plays important role in performance of  $\text{TiO}_2$  layer in DSSC, since it provides good electrical contact between particles, which consequently leads to better electron transfer through the cell, but still restricts unfavorable phase transformation. In this paper two identical cells with natural pigment hypericin as sensitizer were assembled with anodes sintered on two different temperatures ( $500\text{ }^\circ\text{C}$  and  $600\text{ }^\circ\text{C}$ ), so their performance parameters could be compared. The ratios between the maximal power densities ( $P_{\text{max}}$ ) and solar to electrical energy conversion efficiencies ( $\eta$ ) for the two measured cells are 5 times in favor for the cell sintered at  $600\text{ }^\circ\text{C}$ , which shows the importance of temperature treatment of  $\text{TiO}_2$  electrodes for better performance of solar cells.

**Index Terms**— DSSC;  $\text{TiO}_2$  anode; sintering temperature; hypericin.

## I. INTRODUCTION

Dye-sensitized solar cells (DSSC) are very popular due to a low cost of production materials and methods, compared to silicon-based solar cells. They were first introduced in 1991[1] and since then, their performance has been improving [2-4].

The operating principle of DSSC is very simple, as presented in Fig 1. It is designed to mimic photosynthesis in plants. Incident solar photon oxidizes the sensitizer, which further delivers the electron to conduction band of semiconductor. Dye molecule then gets reduced by electrolyte, and electrolyte is further regenerated at the counter electrode. Most common

electrodes for DSSC are  $\text{TiO}_2$  for anode, and platinum electrode as counter one. Widely used electrolyte is  $\text{I}^-/\text{I}_3^-$  solution in acetonitrile[5].

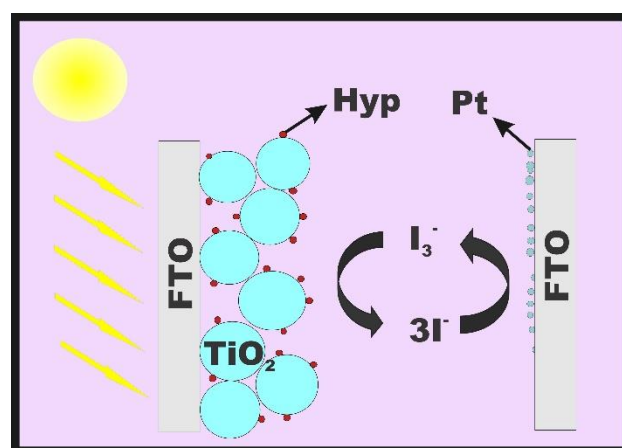


Fig. 1. Schematic representation of DSSC constituent parts

Many types of sensitizers are known and used today: organic, inorganic, synthetic, natural [5]. DSSCs with porphyrin and ruthenium dyes have the highest efficiency of conversion solar energy into electrical, reaching 11 and 13 % [6]. The price and toxicity are great disadvantages of these dyes [7]. On the other hand, natural pigments extracted from flowers, plants and fruits are affordable and widespread, but their efficiency of conversion is only a few percent [8]. The best result published so far for natural pigment sensitized solar cell reported Ghann [9] with pomegranate juice and reached the efficiency of 2 %. In the extensive study by Kumara [10], the best performance showed red turnip, and

Katarina Cvetanović Zobenica is with the University of Belgrade – Institute of Chemistry, Technology and Metallurgy – National Institute of the Republic of Serbia, Njegoševa 12, 11000 Belgrade, Serbia (e-mail: [katarina@nanosys.ihtm.bg.ac.rs](mailto:katarina@nanosys.ihtm.bg.ac.rs)).

Nenad Tadić is with the Faculty of physics, University of Belgrade, Studentski trg 12, 11000 Belgrade, Serbia (e-mail: [nenad.tadic@ff.bg.ac.rs](mailto:nenad.tadic@ff.bg.ac.rs)).

Uroš Lačnjevac is with the Institute for Multidisciplinary Research, University of Belgrade, Kneza Višeslava 1, 11030 Belgrade, Serbia (e-mail: [uroslacnjevac@imsi.bg.ac.rs](mailto:uroslacnjevac@imsi.bg.ac.rs)).

Evgenija Milinković is with the University of Belgrade – Institute of Chemistry, Technology and Metallurgy – National Institute of the Republic of Serbia, Njegoševa 12, 11000 Belgrade, Serbia (e-mail: [evgenija@nanosys.ihtm.bg.ac.rs](mailto:evgenija@nanosys.ihtm.bg.ac.rs)).

Milena Rašljić Rafajilović is with the University of Belgrade – Institute of Chemistry, Technology and Metallurgy – National Institute of the Republic of

Serbia, Njegoševa 12, 11000 Belgrade, Serbia (e-mail: [milena@nanosys.ihtm.bg.ac.rs](mailto:milena@nanosys.ihtm.bg.ac.rs)).

Milče M. Smiljanić is with the University of Belgrade – Institute of Chemistry, Technology and Metallurgy – National Institute of the Republic of Serbia, Njegoševa 12, 11000 Belgrade, Serbia (e-mail: [smilce@nanosys.ihtm.bg.ac.rs](mailto:smilce@nanosys.ihtm.bg.ac.rs)).

Dana Vasiljević-Radović is with the University of Belgrade – Institute of Chemistry, Technology and Metallurgy – National Institute of the Republic of Serbia, Njegoševa 12, 11000 Belgrade, Serbia (e-mail: [dana@nanosys.ihtm.bg.ac.rs](mailto:dana@nanosys.ihtm.bg.ac.rs)).

Dragomir Stanisavljev is with the Faculty of physical chemistry, University of Belgrade, Studentski trg 12, 11000 Belgrade, Serbia (e-mail: [dragisa@ffh.bg.ac.rs](mailto:dragisa@ffh.bg.ac.rs)).

reached cell efficiency was 1,70 % on 470 nm. Still, review papers show that most natural pigments have low performance, with conversion efficiency somewhere between 0,013 and 0,50 % [9].

Hypericin is a photosensitive pigment which is one of the principal active constituents of St. John's wort (*Hypericum perforatum*). Hypericin is novelty in terms of photovoltaics [11], although it is widely used for its photodynamical and phototherapeutic properties in medicine [12]. Hypericin's molecular structure is presented in Fig.2.

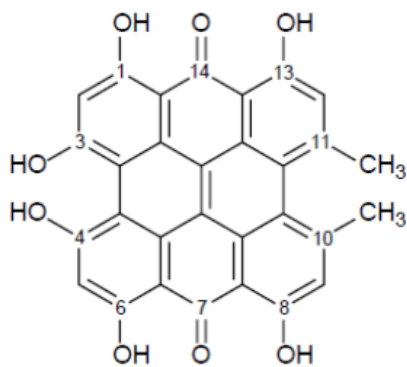


Fig 2. Molecular structure of hypericin.

TiO<sub>2</sub> is a stable, nontoxic oxide, which has a high refractive index (2.4-2.5) and naturally occurs in several crystal forms: rutile, anatase, and brookite. Rutile is the thermodynamically most stable form. Anatase is, however, the preferred structure in DSSCs, because it has a larger bandgap (3.2 vs 3.0 eV for rutile). In recent years, the progress has been made in the development of methods to synthesize new anatase nanostructures such as nanoparticles, nanorods, nanowires and nanotubes [13, 14]. These methods include sol-gel, micelle and inverse micelle, hydrothermal, electrodeposition and many more. One of the most important parameters of fabrication of TiO<sub>2</sub> anode is temperature of sintering, it provides good electrical contact between TiO<sub>2</sub> particles, while, carefully chosen, it does not allow phase transformation from anatase to rutile (~500 °C) [15].

The goal of this paper is to compare the performance of two cells, almost identical, with the difference only in sintering temperature of anode, one at 500 °C, and the other at 600 °C. The motive can be found in the fact that the temperature of 500 °C is recommended as optimal for anatase electrode preparation, but the DSSC devices showed better performance when TiO<sub>2</sub> was sintered at 600 °C, although it showed phase transformation to rutile [16].

## II. EXPERIMENTAL

TiO<sub>2</sub> paste was prepared as described by Ito in ref. [17]. TiO<sub>2</sub> powder (P25, Sigma) was transferred into alumina mortar and grinded, with addition of acetic acid, water and ethanol, respectively. After the transfer into the beaker with ethanol, it was stirred with a magnetic tip and sonicated with an ultrasonic horn. After this set of treatments, terpineol was added, and the mixing and sonication procedure was repeated. Then, the ethyl

cellulose was added, and the sonication treatment was performed once more. At the end, the paste was evaporated from solvents.

TiO<sub>2</sub> paste was coated onto fluorine doped thin oxide glass (FTO), previously cleaned and treated with UV lamp and TiCl<sub>4</sub> treatment, by screen-printing. The photoanodes were then gradually heated under an airflow at 325 °C for 5 min, at 375 °C for 5 min, at 450 °C for 15 min and 500 °C for 15 min. One more step was performed on the electrode sintered at higher temperature – 600°C for 30 min. The exact temperature at the sample position was measured with a K-type thermocouple, Ni/NiCr.

The thickness of the TiO<sub>2</sub> layer was measured on comparator Iskra NP37 (15 μm).

X-ray diffraction (XRD) measurements were performed. (phase composition) using Rigaku Ultima IV X-ray diffraction instrument in thin film geometry with grazing incidence angle of 0.5°, using Ni-filtered CuKα radiation (λ = 1.54178 Å). Obtained data was analyzed with PDXL 2 software. Afterwards, the TiCl<sub>4</sub> treatment was conducted once again on TiO<sub>2</sub> anodes. Right after programmed heating to 500 °C/600 °C and cooling at 80 °C, the electrode was immersed into 10<sup>-4</sup> M hypericin solution in acetone and kept at room temperature for 20 h.

The counter electrode was prepared on cleaned FTO glass, and treated with a solution of HCl in ethanol. Then, after heating at 400 °C a drop of H<sub>2</sub>PtCl<sub>6</sub> solution in ethanol was applied and heated under an airflow again at 400 °C [17]. I<sup>-</sup>/I<sub>3</sub><sup>-</sup> electrolyte solution in acetonitrile was also prepared.

TiO<sub>2</sub> electrode, sensitized with hypericin, counter Pt electrode were assembled as a sandwich type cell with the sealing tape. A drop of electrolyte was put onto the hole on the Pt counter electrode, and then the cells were ready for measurements.

Photovoltaic characteristics of DSSC were examined with the solar simulator Abet, LS series 10500 at 1.5 AM, at 23 °C (measured with IR thermometer) controlled with circular thermostat Julabo F12 (under illumination).

Illumination of the system produces additional heat, so the assembled solar cell was thermostated at the steady state temperature of 23 ± 1 °C. After achieving steady state temperature, photovoltaic measurement was performed by Gamry electrochemical devise, Gamry Series G 300 potentiostat, with Linear sweep voltammetry (LSV).

## III. RESULTS

The aim of this research was to investigate the influence of sintering temperature of TiO<sub>2</sub> layer on the performance of DSSCs with hypericin. Two identically prepared TiO<sub>2</sub> anodes were sintered at different temperatures—500 and 600 °C.

As seen in Fig. 3., XRD patterns of the two anodes feature three different peaks, from left to right: anatase form, substrate and rutile phase. The XRD measurements were performed to ensure that the majority of crystalline form is anatase, which was proven as better choice for DSSC than rutile even at 600 °C.

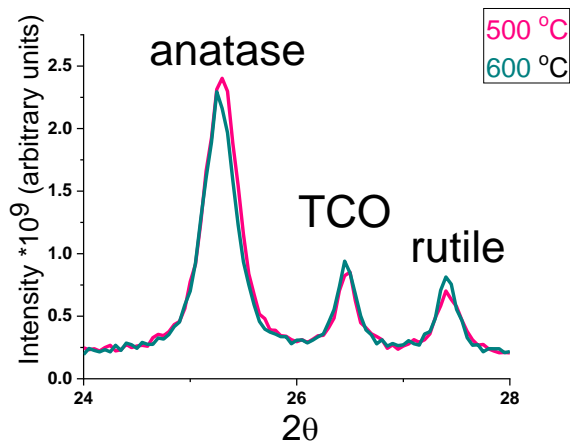


Fig. 3. Fractions of different crystal phases of TiO<sub>2</sub> and substrate TCO, sintered at 500 and 600 °C.

Current density–voltage curves for the cells with anodes sintered at two different temperatures are presented in Fig. 4 and Fig. 5.

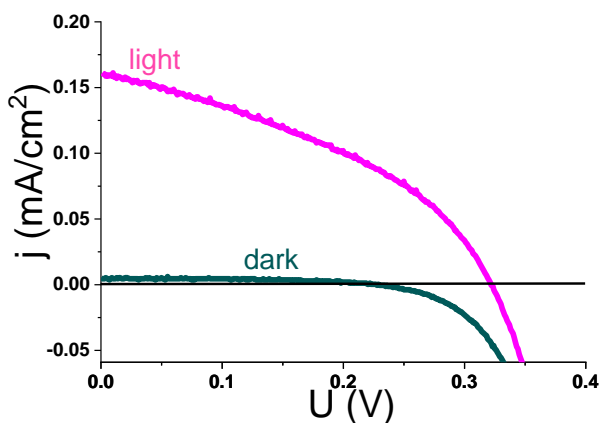


Fig.4. Current density–voltage characteristics of the cell sintered at 500 °C in the dark and under 100 mW cm<sup>-2</sup> of simulated AM1.5 illumination for the illuminated device.

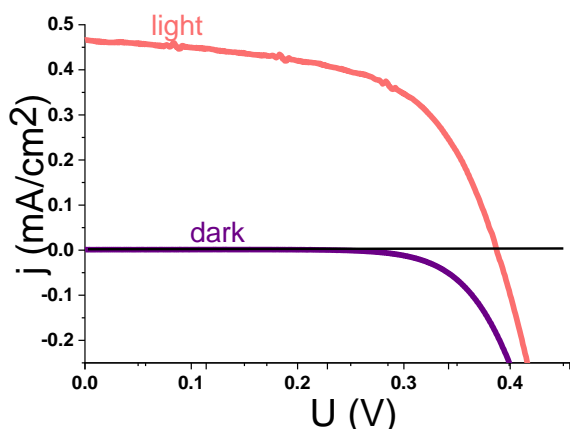


Fig.5. Current density–voltage characteristics of the cell sintered at 600 °C in the dark and under 100 mW cm<sup>-2</sup> of simulated AM1.5 illumination for the illuminated device.

Comparing Fig. 4 and 5 it is noticeable, that the cell with the anode sintered at the higher temperature has far better performance. It has higher values for short circuit current density ( $j_{sc}$ ) and open circuit voltage ( $U_{oc}$ ). For better insight, the cells' performance parameters are given in Table 1 below.

TABLE I  
IE CURVES PARAMETERS FOR MEASURED CELLS

	500 °C	600 °C
$j_{sc}$ (mA/cm <sup>2</sup> )	0.162	0.468
$U_{oc}$ (mV)	322	387
$P_{max}$ (μW/cm <sup>2</sup> )	20.7	106.1
FF	39.7	58.6
$\eta$ (%)	0.021	0.106

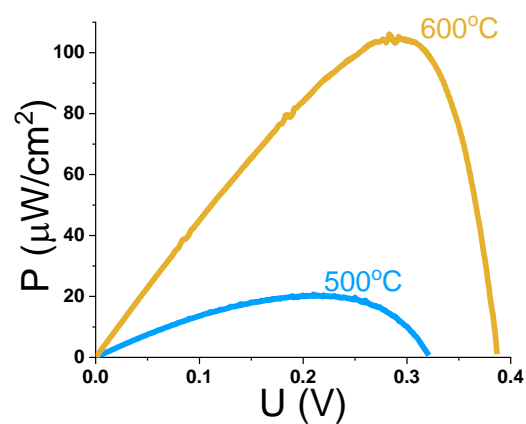


Fig.6. Power density–voltage characteristics of the cells sintered at 500 °C and 600 °C under 100 mW cm<sup>-2</sup> of simulated AM1.5 illumination.

The ratios between the maximal power densities ( $P_{max}$ ) and solar to electrical energy conversion efficiencies ( $\eta$ ) for the two measured cells are 5 times in favor for the cell sintered at 600 °C, as seen in Fig. 6. It shows the importance of temperature treatment of TiO<sub>2</sub> electrodes for better performance of solar cells.

#### IV. CONCLUSION

The goal of this work was to present the importance of sintered temperature for an adequate performance of TiO<sub>2</sub> electrodes in dye sensitized solar cells. Two identical cells, with natural pigment hypericin as sensitizer and different sintered temperature were compared. The result showed five times higher value of maximal power density for the cell with the higher sintering temperature of 600 °C at given conditions. Despite that much lower temperature of electrode preparation is recommended in literature, obtained results show that anatase phase may be preserved even at much higher temperatures, depending of heating procedure. The reason for better performance of the cell treated with higher temperature is better electrical contact between TiO<sub>2</sub> particles, which provided better electron transfer through the anode, and

therefore lower resistance of the cell. This experiment was conducted on P25 TiO<sub>2</sub> particles, but it would be interesting to observe and compare optimal sintering temperatures for other nanostructures such as nanoparticles, nanorods, nanowires, nanotubes, etc.

#### ACKNOWLEDGMENT

This was financially supported by the Ministry of Education, Science and Technological Development of the Republic of Serbia (Grant No. 451-03-68/2020-14/200026 and OI172015).

#### REFERENCES

- [1] B. O'Regan and M. Grätzel, "A low-cost, high-efficiency solar cell based on dye-sensitized colloidal TiO<sub>2</sub> films," *Nature*, vol. 353, pp. 737-740, 1991.
- [2] M. Grätzel, "Dye-sensitized solar cells," *Journal of Photochemistry and Photobiology C: Photochemistry Reviews*, vol. 4, pp. 145-153, 2003.
- [3] J. Gong, K. Sumathy, Q. Qiao, and Z. Zhou, "Review on dye-sensitized solar cells (DSSCs): Advanced techniques and research trends," *Renewable and Sustainable Energy Reviews*, vol. 68, Part 1, pp. 234-246, 2017.
- [4] C.-P. Lee, R. Y.-Y. Lin, L.-Y. Lin, C.-T. Li, T.-C. Chu, S.S. Sun, "Recent progress in organic sensitizers for dye-sensitized solar cells," *RSC Advances*, vol. 5, pp. 23810-23825, 2015.
- [5] A. Hagfeldt, G. Boschloo, L. Sun, L. Kloo, and H. Pettersson, "Dye-Sensitized Solar Cells," *Chemical Reviews*, vol. 110, pp. 6595-6663, 2010.
- [6] F. Gao, Y. Wang, D. Shi, J. Zhang, M. Wang, X. Jing, "Enhance the Optical Absorptivity of Nanocrystalline TiO<sub>2</sub> Film with High Molar Extinction Coefficient Ruthenium Sensitizers for High Performance Dye-Sensitized Solar Cells," *Journal of the American Chemical Society*, vol. 130, pp. 10720-10728, 2008.
- [7] R. E. Yasbin, C. R. Matthews, and M. J. Clarke, "Mutagenic and toxic effects of ruthenium," *Chemico-Biological Interactions*, vol. 31, pp. 355-365, 1980.
- [8] G. Calogero, G. Di Marco, S. Cazzanti, S. Caramori, R. Argazzi, A. Di Carlo, "Efficient dye-sensitized solar cells using red turnip and purple wild sicilian prickly pear fruits," *International journal of molecular sciences*, vol. 11, pp. 254-267, 2010.
- [9] W. Ghann, H. Kang, T. Sheikh, S. Yadav, T. Chavez-Gil, F. Nesbitt, "Fabrication, Optimization and Characterization of Natural Dye Sensitized Solar Cell," *Scientific Reports*, vol. 7, p. 41470, 2017.
- [10] N. T. R. N. Kumara, A. Lim, C. M. Lim, M. I. Petra, and P. Ekanayake, "Recent progress and utilization of natural pigments in dye sensitized solar cells: A review," *Renewable and Sustainable Energy Reviews*, vol. 78, pp. 301-311, 2017.
- [11] K. Cvetanovic Zobenica, U. Lacnjevac, M. Etinski, D. Vasiljevic-Radovic, and D. Stanisavljev, "Influence of the electron donor properties of hypericin on its sensitizing ability in DSSCs," *Photochemical & Photobiological Sciences*, vol. 18, pp. 2023-2030, 2019.
- [12] G. M. Calixto, J. Bernegossi, L. M. de Freitas, C. R. Fontana, and M. Chorilli, "Nanotechnology-Based Drug Delivery Systems for Photodynamic Therapy of Cancer: A Review," *Molecules*, vol. 21, p. 342, 2016.
- [13] J.-Y. Liao, J.-W. He, H. Xu, D.-B. Kuang, and C.-Y. Su, "Effect of TiO<sub>2</sub> morphology on photovoltaic performance of dye-sensitized solar cells: nanoparticles, nanofibers, hierarchical spheres and ellipsoid spheres," *Journal of Materials Chemistry*, vol. 22, pp. 7910-7918, 2012.
- [14] N. Tasić, Z. Marinković Stanojević, Z. Branković, U. Lačnjevac, V. Ribić, M. Žunić, "Mesoporous films prepared from synthesized TiO<sub>2</sub> nanoparticles and their application in dye-sensitized solar cells (DSSCs)," *Electrochimica Acta*, vol. 210, pp. 606-614, 2016.
- [15] S. P. R. Petrović, Ljiljana; Grbić, Boško; Radić, Nenad; Dostanić, Jasmina; Stojadinović, Stevan; Vasilic, Rastko, "Morphology and fractal dimension of TiO<sub>2</sub> thin films," *Macedonian Journal of Chemistry and Chemical Engineering*, vol. 32, p. 9, 2013.
- [16] Y.-F. Chen, C.-Y. Lee, M.-Y. Yeng, and H.-T. Chiu, "The effect of calcination temperature on the crystallinity of nanopowders," *Journal of Crystal Growth*, col 247, pp. 363-370, 2003.
- [17] S. Ito, P. Chen, P. Comte, M. K. Nazeeruddin, P. Liska, P. Péchy, *et al.*, "Fabrication of screen-printing pastes from TiO<sub>2</sub> powders or dye-sensitized solar cells," *Progress in Photovoltaics: Research and Applications*, vol. 15, pp. 603-612, 2007.